



TYPE 1 P.C.C. MEDIAN CURB

REINFORCING
(NOTE 3)

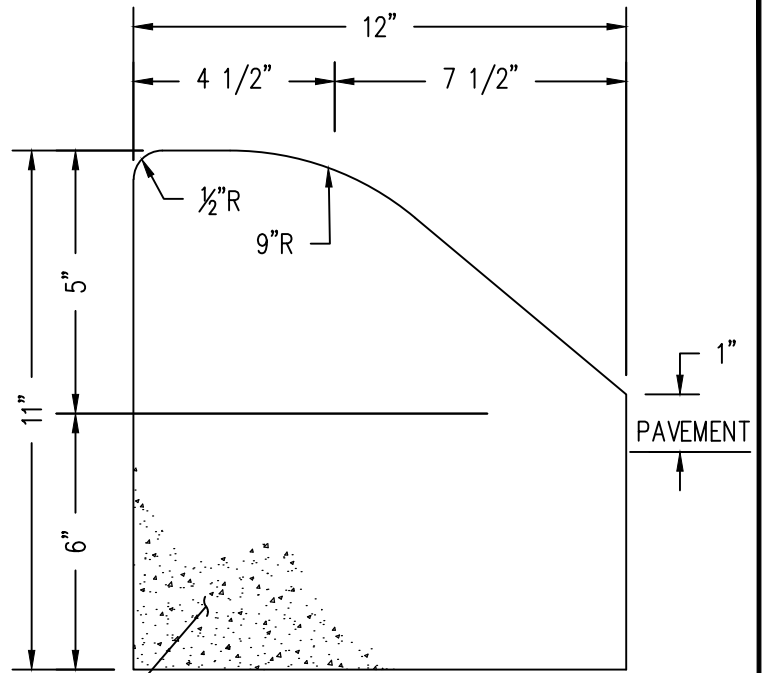

TYPE 3 P.C.C. MEDIAN CURB

REINFORCING
(NOTE 3)

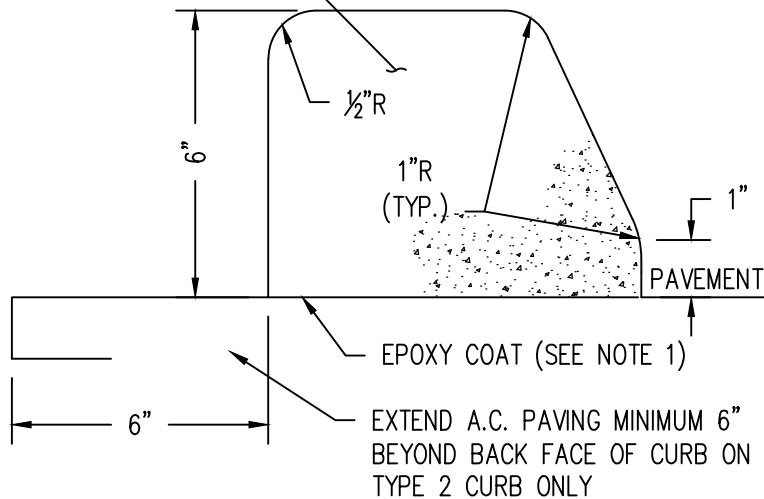

TYPE 2 P.C.C. MEDIAN CURB

EPOXY COAT (SEE NOTE 1)

EXTEND A.C. PAVING MINIMUM 6"
BEYOND BACK FACE OF CURB ON
TYPE 2 CURB ONLY

NOTES:

1. AN APPROVED EPOXY COAT BETWEEN THE CURB PAVEMENT SURFACE SHALL BE USED.
2. SEE NOTES FOR TYPE I CURB AND GUTTER, DRAWING No. W-131B.
3. ALL CONCRETE FOR TYPE 1, TYPE 2 OR TYPE 3 P.C.C. MEDIAN CURB SHALL BE REINFORCED COLLATED, FIBRILLATED, POLYPROPYLENE FIBERS AS MANUFACTURED BY FIBERMESH, OR APPROVED EQUAL, AND SHALL BE ADDED AT A RATE OF 1.5 LBS PER CUBIC YARD OF CONCRETE.
4. ALL NOSES ON MEDIAN CURB SHALL BE POURED SOLID FOR THE FULL WIDTH OF THE MEDIAN.
5. PORTLAND CEMENT CONCRETE (PCC) SHALL BE A MINIMUM 4000 PSI COMPRESSIVE STRENGTH @ 28 DAYS WITH MINIMUM 6.25 SACKS OF TYPE II CEMENT (588 LBS) PER CUBIC YARD OF CONCRETE, A MAXIMUM WATER/CEMENT RATIO OF 0.45, 4.5-7.5% AIR ENTRAINMENT, AND SLUMP SHALL RANGE FROM A MINIMUM OF 1" TO A MAXIMUM OF 4".

DATE	REVISIONS



STANDARD DETAILS FOR PUBLIC WORKS CONSTRUCTION

P.C.C. MEDIAN CURB

SECTION NUMBER: 100
DRAWING NUMBER: W-137
DATE: 2/21/2022